



Aluminium Alloy - 6005A - T6 Extrusion

SPECIFICATIONS

Commercial	6005A
EN	6005A

Aluminium alloy 6005A is a medium strength, heat treatable alloy with excellent corrosion resistance.

Alloy 6005 has properties between those of alloys 6061 and 6082 and can sometimes be used interchangeably with these alloys, but 6005 has better extrusion characteristics and a better mill surface finish. It is difficult to produce thin-wall or complicated extrusions in 6005, but it is still more extrudable than 6082.

6005A tube has very good bending properties.

Applications

6005 and 6005A typically find application in intricate extrusions like:

- ~ Tubing for furniture
- ~ Railway and bus profile structures
- ~ Pylons, platforms and pipelines
- ~ Portable ladders
- ~ Sections where greater strength is needed than given by 6060 and 6063

CHEMICAL COMPOSITION

BS EN 573-3:2009
Alloy 6005

Element	% Present
Silicon (Si)	0.5 - 0.9
Magnesium (Mg)	0.4 - 0.7
Manganese (Mn)	0.5 max
Manganese + Chromium (Mn+Cr)	0.12 - 0.5
Iron (Fe)	0.35 max
Chromium (Cr)	0.3 max
Copper (Cu)	0.3 max
Zinc (Zn)	0.2 max
Others (Total)	0.15 max
Titanium (Ti)	0.1 max
Other (Each)	0.05 max
Aluminium (Al)	Balance

ALLOY DESIGNATIONS

Aluminium alloy 6005A also corresponds to the following standard designations and specifications **but may not be a direct equivalent:**

A96005
AlSiMg
AlSiMg(A)

TEMPER TYPES

The most common temper for 6005 aluminium is:

- T6 - Solution heat treated and artificially aged

SUPPLIED FORMS

Alloy 6005 is supplied as

- Extrusions
- Tube

GENERIC PHYSICAL PROPERTIES

Property	Value
Density	2.70 g/cm ³
Melting Point	605 °C
Thermal Expansion	24 x10 ⁻⁶ /K
Modulus of Elasticity	70 GPa
Thermal Conductivity	188 W/m.K
Electrical Resistivity	0.034 x10 ⁻⁶ Ω .m

MECHANICAL PROPERTIES

BS EN 755-2:2008
Rod & Bar
up to 25mm Dia. & A/F

Property	Value
Proof Stress	225 Min MPa
Tensile Strength	270 Min MPa
Elongation A50 mm	8 %
Shear Strength	205 MPa
Hardness Brinell	90 HB
Elongation A	10 Min %

Above values are for T6 temper



Aluminium Alloy - 6005A - T6 Extrusion

BS EN 755-2:2008
Rod & Bar
25mm to 50mm Dia. & A/F

Property	Value
Proof Stress	225 Min MPa
Tensile Strength	270 Min MPa
Hardness Brinell	90 HB
Elongation A	8 Min %

Above values are for T6 temper

BS EN 755-2:2008
Bar
50mm to 100mm Dia. & A/F

Property	Value
Proof Stress	215 Min MPa
Tensile Strength	260 Min MPa
Hardness Brinell	85 HB
Elongation A	8 Min %

Above values are for T6 temper

BS EN 755-2:2008
Tube
Up To 5mm Wall Thickness

Property	Value
Proof Stress	225 Min MPa
Tensile Strength	270 Min MPa
Elongation A50 mm	6 Min %
Hardness Brinell	90 HB
Elongation A	8 Min %

Above values are for T6 temper

BS EN 755-2:2008
Tube
5mm to 10mm Wall Thickness

Property	Value
Proof Stress	215 Min MPa
Tensile Strength	260 Min MPa
Elongation A50 mm	6 Min %
Hardness Brinell	85 HB
Elongation A	8 Min %

Above values are for T6 temper

BS EN 755-2:2008
Open Profile
Up to 5mm Wall Thickness

Property	Value
Proof Stress	225 Min MPa
Tensile Strength	270 Min MPa
Elongation A50 mm	6 Min %
Hardness Brinell	90 HB
Elongation A	8 Min %

Above values are for T6 temper

BS EN 755-2:2008
Open Profile
5mm to 10mm Wall Thickness


Property	Value
Proof Stress	215 Min MPa
Tensile Strength	260 Min MPa
Elongation A50 mm	6 Min %
Hardness Brinell	85 HB
Elongation A	8 Min %

Above values are for T6 temper

BS EN 755-2:2008
Open Profile
10mm to 25mm Wall Thickness

Property	Value
Proof Stress	200 Min MPa
Tensile Strength	250 Min MPa
Elongation A50 mm	6 Min %
Hardness Brinell	85 HB
Elongation A	8 Min %

Above values are for T6 temper

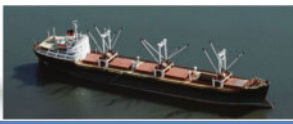

Aluminium Alloy - 6005A - T6 Extrusion

BS EN 755-2:2008
Hollow Profile
Up to 5mm Wall Thickness

Property	Value
Proof Stress	215 Min MPa
Tensile Strength	255 Min MPa
Elongation A50 mm	6 Min %
Hardness Brinell	85 HB
Elongation A	8 Min %

Above values are for T6 temper

BS EN 755-2:2008
Hollow Profile
5mm to 15mm Wall Thickness

Property	Value
Proof Stress	200 Min MPa
Tensile Strength	250 Min MPa
Elongation A50 mm	6 Min %
Hardness Brinell	85 HB
Elongation A	8 Min %

Above values are for T6 temper

WELDABILITY

The weldability of 6005A is excellent. 4043 welding wire is recommended unless joining to one of the 7XXX series. In this case 5356 wire is the suggested alternative.

Weldability – Gas: Excellent
Weldability – Arc: Excellent
Weldability – Resistance: Excellent
Brazability: Excellent

FABRICATION

Workability – Cold: Fair
Machinability: Fair

CONTACT

Address: Wilsons Ltd
Nordic House
Old Great North Road
Huntingdon
PE28 5XN
Tel: +44 (0)1480 456421
Email: sales@wilsonsmetals.com
Web: www.wilsonsmetals.com

REVISION HISTORY

Datasheet Updated 13 November 2018

DISCLAIMER

This Data is indicative only and as such is not to be relied upon in place of the full specification. In particular, mechanical property requirements vary widely with temper, product and product dimensions. All information is based on our present knowledge and is given in good faith. No liability will be accepted by the Company in respect of any action taken by any third party in reliance thereon.

Please note that the 'Datasheet Update' date shown above is no guarantee of accuracy or whether the datasheet is up to date.

The information provided in this datasheet has been drawn from various recognised sources, including EN Standards, recognised industry references (printed & online) and manufacturers' data. No guarantee is given that the information is from the latest issue of those sources or about the accuracy of those sources.

Material supplied by the Company may vary significantly from this data, but will conform to all relevant and applicable standards.

As the products detailed may be used for a wide variety of purposes and as the Company has no control over their use; the Company specifically excludes all conditions or warranties expressed or implied by statute or otherwise as to dimensions, properties and/or fitness for any particular purpose, whether expressed or implied.

Advice given by the Company to any third party is given for that party's assistance only and without liability on the part of the Company. All transactions are subject to the Company's current Conditions of Sale. The extent of the Company's liabilities to any customer is clearly set out in those Conditions; a copy of which is available on request.